

Calcium Carbonate Scale on Pipes: Analysis of Kinetic, Mass, Polymorphim, morphology with chemical inhibitor

by Samsudi Raharjo

Submission date: 01-May-2020 10:37AM (UTC+0700)

Submission ID: 1312825128

File name: netic,_Mass,_Polymorphim,_morphology_with_chemical_inhibitor.pdf (433.32K)

Word count: 1922

Character count: 10344

15

Calcium Carbonate Scale on Pipes: Analysis of Kinetic, Mass, Polymorphism, Morphology with Chemical Inhibitor

19

⁹ 'S. Raharjo, "S. Muryanto, 'J. Jamari and 'A.P. Bayuseno

'Department of Mechanical Engineering, Muhammadiyah University,
Semarang, Indonesia

"Department of Chemical Engineering, UNTAG University, Semarang, Indonesia

'Department of Mechanical Engineering, Diponegoro University, Semarang, Indonesia

Abstract: Scaling of calcium carbonate on the pipes under the influence of citric acid as a chemical inhibitor was investigated in the present study. In the experimental research, the scale-forming solution was prepared by setting equimolar solutions of CaCl₂ and Na₂CO₃ with Ca²⁺ concentration of 3000 ppm. The induction time of scale nucleation was determined by measuring the ion conductivity of the solution flowing out of the pipe. Scale formed on the coupon was then evaluated using SEM/EDX and XRPD rietveld analysis. The presence of citric acid clearly influenced the kinetics of calcium carbonate formation in pipes which was presented as an induction time. The longer induction time was observed when the largest amount of citric acid was added to the solution. The crystalline phase was found to be mostly calcite and vaterite while the scale has a plate-like morphology. The presence of citric acid seems to inhibit the scale deposition and change the morphology of the crystals.

Key words: Calcium carbonate, citric acid, morphology, XRPD rietveld, SEM/EDX, conductivity

INTRODUCTION

Calcium Carbonate (CaCO₃) scaling is commonly discovered on certain pipes of industrial applications including the evaporator and cooling power plants. The scaling of pipes could be regarded as a negative impact on the operational efficiency of the unit and has become a major economic concern in most industries. In general, calcium carbonate is slightly soluble in groundwater and thereby being able to precipitate from the saline water upon heating. Scaling of calcium carbonate may result in three crystal polymorphs in the varying solution condition, namely calcite, vaterite and aragonite which also could be related to the substrate for disposition of the scale. Aragonite and vaterite could be grown on the heated metal surfaces at the lower temperatures, conversely, calcite would be crystallized at the higher temperatures (Muryanto *et al.*, 2012). In addition, minerals of calcium carbonate have been extensively examined because of their relevance in geological, technological and biological environments and systems.

⁸ Further, the scaling of calcium carbonate and their structural, chemical and morphological properties are controlled by the initial supersaturation, temperature, hydrodynamic conditions and the presence of additives (Azimi and Papangelakis, 2010). In this point, the

supersaturated forming solution promotes the first nucleation formation and the contact time (Rabizadeh *et al.*, 2014; Antony *et al.*, 2011). The stable nuclei on the surface are taken to develop the deposit. Moreover, the temperature has a significant factor to encourage the increasing deposition of calcium carbonate on the wall of pipes. In this way, the crystal growth rate is significantly influenced by the increasing temperature.

Furthermore, the formation of calcium carbonate scale may be influenced by the hydrodynamic factor such as a flow rate, pipe diameter and surface roughness (Bahadori, 2010). A previous study by Gourdon (2011) has demonstrated that the scale of calcium carbonate can be grown in full laminar and turbulent flow. In full laminar flow, the crystal growth of deposit is favored at a slow flow rate while in fully turbulent flow, the scale deposit was increasingly grown with the increasing flow fluid rate (Amor *et al.*, 2004).

In the increasing velocity of fluid flow, the more calcium carbonate deposition may occur (Muryanto *et al.*, 2012). In general, the scale deposition follows linear with velocity. The higher velocity can sometimes promote scale deposition on the wall surface of pipes with all sizes ¹⁷ diameter (Hasan *et al.*, 2012). Moreover, crystallization due to the lateral growth of the scale deposit on the membrane surface may result in flux declining and surface

blockage (Lin *et al.*, 2002). Accordingly, the traditional experimental procedures for bulk precipitation, crystal seeding, constant composition or continuous flow processes are commonly employed for changing the properties of the scale.

A method to prevent the formation of the calcium carbonate scale in the pipe may use chemical inhibitors which can control the nucleation and crystal growth and crystal polymorphism and morphology (Mullin, 2004). The use of effective additives may help to reduce the capability of crystal adhered to the wall of pipes and the subsequent processes for washing away of the scale. Correspondingly, all chemical additives selected for preventing scaling should reduce possible the growth rate of scaling. Here, the proper selection of inhibitor is required prior to conducting the necessary steps for scaling mitigation, control and removal (Wu *et al.*, 2010).

This study presents a study on the formation, control and mitigation of the calcium carbonate scale on pipes with a citric acid inhibitor. The variable processes investigated were: temperature (30, 40, 50, 600°C) and the concentration of citric acid additives (5, 10, 20 ppm). The nucleation kinetics were examined through measurement of ion conductivity. The scale deposits were then characterized by XRPD for phase composition and SEM/EDX for morphology and chemical elemental analysis.

MATERIALS AND METHODS

Materials and equipment: For preparing the crystal forming solution, the powder precursor of CaCl and Na CO with the analytical grade (Merck) in that for each powder was diluted in the distilled water. For the

crystallization experiment, 5L of equimolar CaCl and Na CO were prepared in a glass beaker which in turn results in the stock solution with the Ca²⁺ concentration of 3000 ppm. The solutions were then separately transferred in the two vessels and set-up at the required temperature. Subsequently, the citric acid (C₆H₈O₇) with analytical grade was prepared in the solution in an amount of 5, 10 and 20 ppm. In this way, the amount of citric acid additive was diluted into a vessel containing 5 Liters of CaCl₂ solution, then mechanically stirred at 200 rpm to achieve the homogenous mixing solution. The calcium carbonate scale was formed using the pilot-scale equipment shown in Fig. 1. During the experiments, the conductivity of the solution, leaving the test pipe section was continuously measured for up to 2 h. After this, the scale deposited on the wall surface of the test coupons was carefully removed, dried and weighed for subsequent characterization.

Material characterization of the precipitates: The characterization of the precipitates was carried out by XRPD (X-Ray Powder Diffraction) method for phase identification analysis and Scanning Electron Microscopy (SEM-analysis), equipped with EDX for morphology and chemical elemental analysis. In this way, the XRPD data collection was conducted using Cu-K α monochromated radiation in a conventional Bragg-Brentano (BB) θ - θ geometry (D5005 Shimadzu). The scan parameters (5-85° 2 θ , 0.020 steps, 15 sec/step) were documented. A PC-based search-match program (Match Software) was used for possible crystalline phases of precipitates. Further, the SEM examination performed on the sample of the precipitates which were mounted on a circular aluminum holder and finally sputtered with carbon.

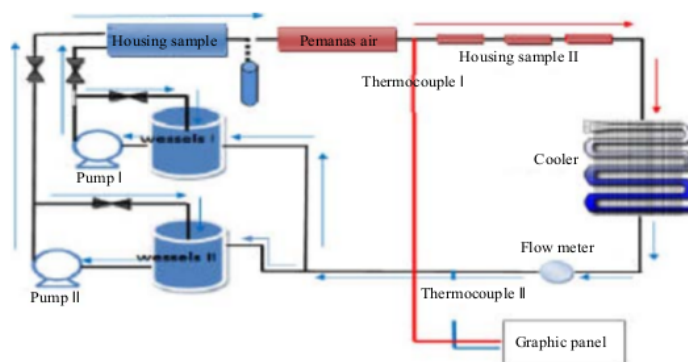


Fig. 1 : Experimental setup used in the calcium carbonate precipitation

RESULTS AND DISCUSSION

Induction time for nucleation of calcium carbonate:

Experimentally, the addition of citric acid (5, 10, 20 ppm) resulted in the change of induction period of calcium carbonate crystallization at room temperature of 30°C (Fig. 2). The induction time of the calcium carbonate system was observed almost doubled in the presence of 5 ppm citric acid (16 min), tripled to 10 ppm (20 min). Moreover, the presence of 20 ppm citric acid (26 min) led to an induction time four times greater than that for in the absence of citric acid system (12 min). This represents a benefit in scaling prevention for a long induction period would result in the postponed scaling process. However, this condition should be corroborated by additional experiments carried out at different temperatures.

Effect of temperature on the mass scale deposition: The scale deposited on the surface of coupon during the experiment was then removed and the yield of the mass scale is presented in Fig. 3. This represents how the scaling rate of calcium carbonate was dependent on the temperature on which the scale formed but once the temperature was increased then the impact of the initial material was significantly increased. The temperature has a strong effect on increasing the mass scales of calcium carbonate. At varying temperature, the respective mass scales were 13, 28, 49 and 80 mg corresponding to a temperature of 300, 400, 500 and 600C, respectively. The results were similar finding for calcium carbonate and

showed that the increasing temperature leads to increasing the mass deposition rate of scales (Muryanto *et al.*, 2012).

The influence of citric acid in the formation of calcium carbonate scale:

The experimental results of citric acid in addition to inhibiting the scaling are presented in Fig. 4. Testing variable concentrations of citric acid (5, 10, 20 ppm) showed a proportional decrease in the mass scales with increasing additive concentration. The mass scales of calcium carbonate yielded in the presence of 5 ppm citric acid was 10 mg. Similarly, 6 mg of the mass scale was precipitated from the solution in the presence of 10 ppm citric acid. The increasing mass scale (13 mg) was also produced at 20 ppm citric acid. Clearly, the presence of citric acid in solution at very low concentrations may adsorb onto the crystal surface and retard the energetically favorable growth positions on the surface, thus, effectively inhibiting further precipitation (Rabizadeh *et al.*, 2014).

Microstructures of calcium carbonate scales: The addition of citric acids also affects the changes of polymorphism and morphology crystals of calcium carbonate. XRPD data of the experiment at a rate of 30 mL/min in the absence and presence of additives citric acid 5, 10, 20 ppm are presented in Fig. 5 and 6. This figure showed that the intensity line formed at an angle 2θ matched with the PDF (Powder Diffraction Pattern) line with number #86-2334 for calcite and PDF#741868 for vaterite. Moreover, the mineralogical phase composition of the scales was also, confirmed through XRPD rietveld method and showed that the scales have consisted of calcite and vaterite. However, calcite may be the most stable phase while vaterite is the metastable one and once the temperature increased, it may transform again into calcite (Muryanto *et al.*, 2012).

As expected, the SEM/EDX analysis showed the high spectrum of Ca, C and O which corresponds to the calcium carbonate while a prismatic to a round shaped crystal morphology was observed. Moreover, the

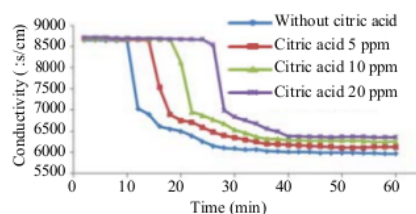


Fig. 2: Induction time measured on the calcium carbonate precipitation

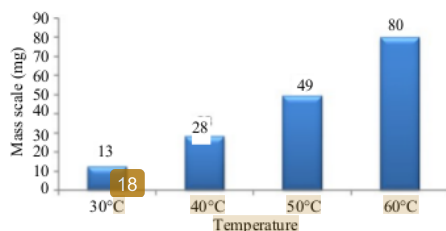


Fig. 3: Effect of temperature on the resulting mass scale formed on pipes

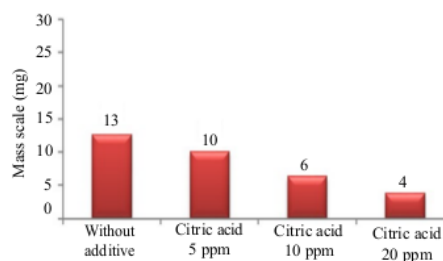


Fig. 4: Effect of the citric acid on the resulting mass scale formed on pipes



Figure 1 consists of four SEM images labeled (a) through (d). Each image includes a scale bar and technical parameters at the bottom. (a) shows large, irregular, flake-like structures. (b) shows smaller, more rounded, and smoother particles. (c) shows even smaller, more uniform, and spherical particles. (d) shows a dense, granular surface composed of many small, rounded particles.

12

The higher temperature set up, the more mass of the scale deposited on pipes indicating that the increasing temperature promoted the scale formation. The crystalline phases of the scale were found to be mostly calcite and vaterite as shown by the XRPD diffractogram. SEM observation of the scales showed crystals with plate-like morphology formed on pipes without additives in the solution. Apparently, this crystal changed to the round shaped morphology in the presence of additive. The change the crystal morphology may relate to citric acid adsorption occurred on the surface of the crystals.

It was found that in all the experiments, the induction period changed in the presence of citric acid in solution.

ACKNOWLEDGEMENT

The researchers express their gratitude to the Universitas Muhamadiyah in Semarang Indonesia for supporting this PhD research project.

REFERENCES

- 3 Amor, M.B., D. Zgolli, M.M. Tlili and A.S. Manzola, 2004. Influence of water hardness, substrate nature and temperature on heterogeneous Calcium carbonate nucleation. *Desalin.*, 166: 79-84.
- Antony, A., J.H. Low, S. Gray, A.E. Childress and P. Le-Clech *et al.*, 2011. Scale formation and control in high pressure membrane water treatment systems: A review. *J. Membr. Sci.*, 383: 1-16.
- 7 Azimi, G. and V.G. Papangelakis, 2010. Thermodynamic modeling and experimental measurement of calcium sulfate in complex aqueous solutions. *Fluid Phase Equilibria*, 290: 88-101.
- Bahadori, A., 2010. Prediction of scale formation in calcium carbonate aqueous phase for water treatment and distribution systems. *Water Qual. Res. J. Can.*, 45: 379-389.
- 6 Gourdon, M., 2011. The effects of flow velocity on crystallization fouling in falling film black liquor evaporators. *Proceedings of International Conference on Heat Exchanger Fouling and Cleaning-2011*, June 5-10, 2011, Technical University of Crete, Crete Island, Chania, Greece, pp: 111-117.
- 5 Hasan, B.O., G.J. Nathan, P.J. Ashman, R.A. Craig and R.M. Kelso, 2012. The effects of temperature and hydrodynamics on the crystallization fouling under cross flow conditions. *Appl. Therm. Eng.*, 36: 210-218.
- 2 Lin, R.Y., J. Y. Zhang and P.X. Zhang, 2002. Nucleation and growth kinetics in synthesizing nanometer calcite. *J. Crystal Growth*, 245: 309-320.
- 2 Mullin, J.W., 2004. *Crystallization*. 4th Edn., Butterworth Heinemann, Boston, Oxford, UK., Pages: 594.
- Muryanto, S., A.P. Bayuseno, W. Sediono and W. Mangestiyono, 2012. Development of a versatile laboratory project for scale formation and control. *Educ. Chem. Eng.*, 8: 8-e84.
- Rabizadeh, T., C.L. Peacock and L.G. Benning, 2014. Carboxylic acids: Effective inhibitors for calcium sulfate precipitation?. *Mineral. Mag.*, 8: 1465-1472.
- Wu, Z., J.H. Davidson and L.F. Francis, 2010. Effect of water chemistry on calcium carbonate deposition on metal and polymer surfaces. *J. Colloid Interface Sci.*, 343: 16-18.

Calcium Carbonate Scale on Pipes: Analysis of Kinetic, Mass, Polymorphism, morphology with chemical inhibitor

ORIGINALITY REPORT

19%

SIMILARITY INDEX

12%

INTERNET SOURCES

16%

PUBLICATIONS

9%

STUDENT PAPERS

PRIMARY SOURCES

- | | | |
|---|---|----|
| 1 | Warsinger, David M., Jaichander Swaminathan, Elena Guillen-Burrieza, Hassan A. Arafat, and John H. Lienhard V. "Scaling and fouling in membrane distillation for desalination applications: A review", Desalination, 2015.
Publication | 1% |
| 2 | Lin, R.y.. "Mass transfer of reactive crystallization in synthesizing calcite nanocrystal", Chemical Engineering Science, 20061106
Publication | 1% |
| 3 | ijesonline.co.in
Internet Source | 1% |
| 4 | francis.cems.umn.edu
Internet Source | 1% |
| 5 | Submitted to Al-Nahrain University
Student Paper | 1% |
| 6 | docplayer.net
Internet Source | 1% |

7	authors.library.caltech.edu Internet Source	1 %
8	Cleo Kosanović, Simona Fermani, Giuseppe Falini, Damir Kralj. "Crystallization of Calcium Carbonate in Alginate and Xanthan Hydrogels", Crystals, 2017 Publication	1 %
9	www.igi-global.com Internet Source	1 %
10	M. Margret, V. Subramanian, R. Baskaran, B. Venkatraman. "Detection of scales and its thickness determination in industrial pipes using Compton backscattering system", Review of Scientific Instruments, 2018 Publication	1 %
11	"Further Readings", Essentials of Oil and Gas Utilities, 2016. Publication	1 %
12	Submitted to School of Business and Management ITB Student Paper	1 %
13	Karen Shafer-Peltier, Colton Kenner, Eric Albertson, Ming Chen, Stephen Randtke, Edward Peltier. "Removing scale-forming cations from produced waters", Environmental Science: Water Research & Technology, 2020	1 %

14

Alessandro F. Gualtieri. "Accuracy of XRPD QPA using the combined Rietveld–RIR method", *Journal of Applied Crystallography*, 2000

Publication

1 %

15

sintadev.ristekdikti.go.id

Internet Source

1 %

16

Euis Hidayah, Okik Cahyonugroho. "Assessment of Organic Fraction Based on Its Molecular Weight and Disinfection by-Product Formation Through Different Coagulant", *Journal of Ecological Engineering*, 2019

Publication

1 %

17

Submitted to Washington University in St. Louis

Student Paper

1 %

18

etheses.saurashtrauniversity.edu

Internet Source

<1 %

19

W. Mangestiyono, J. Jamari, S. Muryanto, A. P. Bayuseno. " CaSO Scale Formation on Vibrated Piping System in the Presence Citric Acid ", *E3S Web of Conferences*, 2018

Publication

<1 %

